



LB/D001/02/10
DCU 03/21

RICE HUSK BASED ADSORBENTS FOR DYE REMOVAL FROM WASTEWATER

LIBRARY
UNIVERSITY OF MORATUWA, SRI LANKA
MORATUWA

MASTER OF SCIENCE

G.K. JAYATUNGA

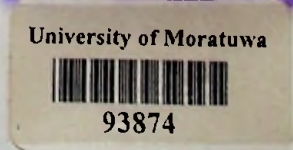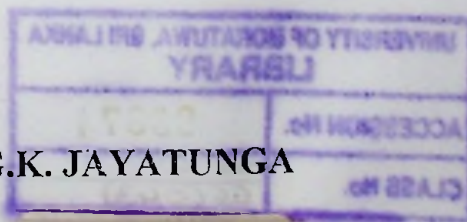

66 "09"

66(043)
TH

UNIVERSITY OF MORATUWA
SRI LANKA

AUGUST 2009

93874
(with CD-Rom)

RICE HUSK BASED ADSORBENTS FOR DYE REMOVAL FROM WASTE WATER

By

G.K. JAYATUNGA

THIS THESIS WAS SUBMITTED TO THE
DEPARTMENT OF CHEMICAL AND PROCESS ENGINEERING
OF THE UNIVERSITY OF MORATUWA
IN PARTIAL FULFILLMENT OF THE REQUIREMENT FOR THE
DEGREE OF MASTER OF SCIENCE

66 "09"
66(043)
TH

DEPARTMENT OF CHEMICAL AND PROCESS ENGINEERING
UNIVERSITY OF MORATUWA
MORATUWA
SRI LANKA

AUGUST 2009



DECLARATION

The work submitted in this dissertation is the result of my own investigation, except where otherwise stated. It has not already been accepted for any degree, and is also not being concurrently submitted for any other degree or diploma in any university the best of my knowledge and belief it does not contain any material previously published, written or orally communicated by another person

UOM Verified Signature

.....
G.K.Jayatunga

19th August 2009

I endorse the declaration by the candidate.

UOM Verified Signature

Supervisor

ACKNOWLEDGEMENT

It is a great pleasure to express gratitude to those who were behind me in completing my works successfully.

Thanks are due first to my supervisor, Dr. (Mrs.) Padma Amarasinghe, Senior Lecturer, Department of Chemical & Process Engineering, University of Moratuwa, for her great insights and perspectives. Then I must offer my sincere thanks to Dr.(Ms). Maneesha Gunsekara and Dr. Shantha Walpolage, Senior Lecturer, Department of Chemical & Process Engineering, University of Moratuwa, for the valuable comments given, as my progress review committee members

Dr. Jagath Premachandra, Head of the Chemical & Process Engineering Department and all the lecturers of the Department of Chemical & Process Engineering, University of Moratuwa, who helped me in various ways to complete this successfully, must be specially mentioned. Then I am very much grateful to the University Research Grants and National Science Foundation for providing me the research funding and Post Graduate Studies Division, University of Moratuwa for approving my research project.

Ms. Dinusha Martino of Environmental Engineering laboratory and all the staff of Energy Engineering, Chemistry, Polymer Engineering, Food & Microbiology laboratories, Department of Chemical & Process Engineering, University of Moratuwa are reminded with heartfelt of thanks for their support given me in various occasions.

I would like to extend my sincere gratitude to my colleague Mr. Kasun Udana who was in MAS Active Linea Intimo for providing necessary dyes stuffs and “Rice mill”, Minuwangoda and Rice Research Institute, Batalegoda for providing rice husk throughout the research, without which I couldn't carry my research

Finally I would be thankful to all my colleagues Ms. Dilini Dhanusekara, Ms. Gayanee Karunarathna, Ms Irosha Kularathna, Ms. Kumuduni Abesinghe, Mr. Rasika Eranda and Ms. Thanuja Pathiraja who were with me and gave the best support me to successful this event by making the research period pleasant and enjoyable.

CONTENTS

DECLARATION.....	i
ACKNOWLEDGEMENT.....	ii
CONTENTS	iii
TABLES	vi
FIGURES	vii
ABBREVIATIONS.....	ix
ABSTRACT	x
CHAPTER 1: INTRODUCTION	1
1.1 TEXTILE EFFLUENT	1
1.2 TECHNOLOGIES AVAILABLE FOR COLOR REMOVAL	2
1.3 OBJECTIVE OF THE RESEARCH.....	4
1.4 SIGNIFICANCE OF THE PROJECT.....	5
CHAPTER 2: LITERATURE REVIEW	6
2.1 ADSORPTION.....	6
2.2 ADSORBENT	7
2.2.1 Activated Carbon.....	7
2.3 ADSORPTION KINETICS.....	8
2.3.1 The First Order Kinetic Model	8
2.3.2 The Second Order Kinetic Model	9
2.4 ADSORPTION ISOTHERMS	9
2.4.1 Langmuir Isotherm	9
2.4.2 Freundlich Isotherm	10
2.4.3 Tempkin Isotherm	11
2.5 MODES OF ADSORPTION.....	11
2.5.1 Single Stage Operation.....	11
2.5.2 Multistage Crosscurrent Operation	13
2.5.3 Multistage Countercurrent Operation.....	14
2.5.4 Fixed Bed Adsorption	14
2.5.4.1 Length of Unused Bed.....	16
2.5.4.2 Scale up Theory.....	17

2.6	RICE HUSK	19
2.7	PAST STUDIES ON REMOVAL OF DYES	21
2.7.1	Preparation of Adsorbent.....	23
2.7.2	Effect of Parameters.....	25
2.7.3	Adsorption Kinetics.....	27
2.7.4	Adsorption Isotherms.....	27
2.7.5	Fixed Bed Adsorption Test.....	27
CHAPTER 3: METHODOLOGY.....		29
3.1	RAW MATERIAL	29
3.2	ADSORBATES	29
3.3	FACILITIES.....	29
3.4	ADSORBENT PREPARATION	30
3.4.1	Nominal Treatment.....	30
3.4.2	Physical Treatment	30
3.4.3	Chemical Treatment	31
3.4.4	Chemical- Thermal Treatment	31
3.4.5	Thermal Treatment	31
3.5	BATCH EXPERIMENTS	33
3.5.1	Effect of Type of Rice Husk.....	33
3.5.2	Effect of Amount of Adsorbent Dosage.....	34
3.5.3	Effect of Particle Size.....	34
3.5.4	Effect of PH.....	35
3.5.6	Effect of Concentration of Dye Solution.....	35
3.5.7	Adsorption Isotherms	35
3.6	FIXED BED EXPERIMENTS.....	36
3.7	REAL TEXTILE WASTEWATER TREATMENT	37
CHAPTER 4: RESULTS AND DISCUSSION		39
4.1	EFFECT OF TYPE OF RICE HUSK	40
4.2	PHYSICAL TREATMENT	41
4.3	CHEMICAL TREATMENT	42
4.4	CHEMICAL-THERMAL TREATMENT	43
4.5	THERMAL TREATMENT.....	44
4.5.1	Effect of Carbonizing Temperature.....	44

4.5.2 Effect of Carbonizing Time.....	45
4.5.3 Carbon Yield	46
4.6 EFFECT OF ADSORBENT DOSAGE	47
4.7 EFFECT OF PARTICLE SIZE	49
4.8 EFFECT OF PH	50
4.9 EFFECT OF CONTACT TIME.....	51
4.10 EFFECT OF CONCENTRATION OF DYE SOLUTION	55
4.11 ADSORPTION KINETICS.....	59
4.12 ADSORPTION ISOTHERMS	64
4.13 FIXED BED EXPERIMENTS.....	68
4.14 REAL TEXTILE WASTEWATER TREATMENT	70
4.15 SCALE UP	70
CHAPTER 5: CONCLUSION.....	73
REFERENCES.....	75
ANNEXES	79
1. Calibration Curve for Nylosan Blue.....	79
2. Calibration Curve for Malachite Green.....	79
3. Equilibrium Data	80
4. Kinetic Data.....	82

TABLES

Table 1.1: Principal Existing and Emerging Processes for Dye Removal	2
Table 2.1: Typical composition of rice husk	19
Table 2.2: Chemical composition of mineral ash from rice husk.....	20
Table 2.3: Reported characteristics of rice husk	20
Table 2.4: Past studies carried out to test various adsorbents for specific dyes.....	21
Table 2.5: Rice Husk Based Adsorbent Prepared from Different Methods.....	23
Table 2.6: Rice Husk Based Adsorbent Prepared from Chemical- Thermal Activation	24
Table 2.7: Previous studies on effect of adsorbate pH	25
Table 3.1: Summary of adsorbent preparation methods.....	32
Table 3.2: Rice Varieties Available in Sri Lanka.....	34
Table 4.1: Adsorption capacity of dye on to different varieties of raw rice husk available in Sri Lanka.....	41
Table 4.2: Adsorption capacity and % removal of dyes.....	42
Table 4.3: Effect of activation time on Carbon Yield	46
Table 4.4: First and second order parameters.....	60
Table 4.5: Langmuir, Freundlich and Tempkin isotherm parameters	64
Table 4.6: Comparison of Treatment Methods.....	66
Table 4.7: Bed capacity & LUB with varying adsorbent	69
Table 4.8: Results of batch experiments with real waste water	70
Table 4.9: Pilot scale parameters for batch operation	71
Table 4.10: Pilot scale parameters for RRH in fixed bed operation.....	71
Table 4.11: Pilot scale parameters for BRH in fixed bed operation.....	71
Table 4.12: Pilot scale parameters for TRH700 in fixed bed operation.....	72
Table 4.13: Summarized pilot scale parameters for fixed bed operation.....	72

FIGURES

Fig 2.1: Single stage adsorption	12
Fig 2.2: Two stage cross current adsorption.....	13
Fig 2.3: Countercurrent Multistage Adsorption	14
Fig 2.4: Fixed bed adsorption.....	15
Fig 2.5: Breakthrough curve.....	16
Fig 2.6: Breakthrough curve.....	18
Fig 3.1: Batch experimental setup.....	33
Fig 3.2: Experimental fixed bed adsorption column	36
Fig 3.3: Schematic diagram of the experimental fixed bed adsorption column.....	37
Fig 4.1: Effect of type of rice husk on dye adsorption	40
Fig 4.2: Effect of type of treatment on dye adsorption.....	42
Fig 4.3: Effect of concentration of phosphoric acid solution in chemically treated RRH.....	43
Fig 4.4: Effect of concentration of phosphoric acid in chemically- thermally treated adsorbent.....	43
Fig 4.5: Effect of carbonization temperature of TRH for both dyes	44
Fig 4.6: Effect of carbonization time of TRH for adsorption of MG & NB	45
Fig 4.7: Effect of carbonization time of TRH for adsorption of NB.....	45
Fig 4.8: Effect of carbonization time of TRH for adsorption of MG.....	46
Fig 4.9: Effect of adsorbent dose on adsorption of MG and NB on to RRH	48
Fig 4.10: Effect of amount of adsorbent dose of RRH on MG uptake.....	48
Fig 4.11: Effect of particle size on the adsorption of MG on to the RRH.....	49
Fig 4.12: Effect of particle size on the adsorption of NB on to the RRH	50
Fig 4.13: Effect of pH on dye adsorption on to RRH, Initial concentration 30 mg/l.....	50
Fig 4.14: Effect of contact time for the uptake of MG & NB by RRH.....	51
Fig 4.15: Effect of contact time for the uptake of NB & MG by TRH700	52
Fig 4.16: Effect of contact time for the uptake of NB & MG by GAC.....	52
Fig 4.17: Effect of contact time for the uptake of NB & MG by BRH.....	53
Fig 4.18: Effect of contact time for the uptake of NB & MG by ARH.....	53
Fig 4.19: Effect of contact time for the uptake of NB & MG by 60PRH	54
Fig 4.20: Effect of contact time for the uptake of NB & MG by 60PTRH.....	54
Fig 4.21: Effect of initial concentration on adsorption capacity of NB & MG onto RRH	55

Fig 4.22: Effect of initial concentration on adsorption capacity of NB & MG onto TRH700	56
Fig 4.23: Effect of initial concentration on adsorption capacity of NB & MG onto BRH	56
Fig 4.24: Effect of initial concentration on adsorption capacity of NB onto RRH	57
Fig 4.25: Effect of initial concentration on adsorption capacity of MG onto RRH	57
Fig 4.26: Effect of initial concentration on % removal of NB & MG onto RRH	58
Fig 4.27: Effect of initial concentration on % removal of NB & MG onto BRH	58
Fig 4.28: Effect of initial concentration on % removal of NB & MG onto TRH700 ...	59
Fig 4.29: Second order kinetic plot for NB adsorption on TRH700, GAC & RRH	61
Fig 4.30: Second order kinetic plot for NB adsorption on ARH & BRH	61
Fig 4.31: Second order kinetic plot for NB adsorption on 60PTRH & 60PRH	62
Fig 4.32: Second order kinetic plot for MG adsorption on RRH, TRH700 & GAC.....	62
Fig 4.33: Second order kinetic plot for MG adsorption on 60PTRH & 60PRH	63
Fig 4.34: Second order kinetic plot for MG adsorption on ARH & BRH.....	63
Fig 4.35: Langmuir isotherm plot for adsorption of MG on RRH, TRH700 & BRH ..	65
Fig 4.36: Freundlich isotherm plot for adsorption of NB on BRH & ARH.....	65
Fig 4.37: Freundlich isotherm plot for adsorption of NB on to TRH700 & RRH	66
Fig 4.38: Effect of Type of treatment on percentage of dye removal	67
Fig 4.39: Effect of Type of treatment on dye adsorption capacity.....	67
Fig 4.40: Break through curve for NB.....	68
Fig 4.41: Break through curve for MG.....	69

ABBREVIATIONS

ABSTRACT

- RRH- raw rice husk
- BRH- base washed rice husk
- ARH- acid washed rice husk
- PRH- phosphoric acid treated rice husk
- PTRH- phosphoric acid treated thermally activated rice husk
- TRH- thermally activated rice husk
- TRH700- thermally activated rice husk at 700°C for 1 hour
- 60PTRH- 60% v/v phosphoric acid treated thermally activated rice husk
- MG- Malachite green
- NB- Nylosan blue
- GAC- commercially available granular activated carbon
- LUB- Length of the unused bed

Adsorption of textile dyes onto rice husk based adsorbents from aqueous solutions was studied. Batch experiments were conducted to determine the effect of method of treatment of rice husk on adsorption. Raw rice husk, chemically or thermally activated rice husk were tested for adsorption of Malachite green and Nylosan blue. The maximum adsorption was observed at solution pH values above 6 for Malachite green and below 3 for Nylosan blue. The adsorbent to solution ratio, solution dye concentration, contact time and adsorbent particle size affect the degree of dye removal. Carbonizing at 700°C for 1 hr was observed as the optimum condition for thermal activation. Base washed rice husk and thermally activated rice husk showed high adsorption capacities compared to acid washed rice husk, phosphoric acid treated rice husk and raw rice husk. Malachite green dye showed high adsorption compared to Nylosan blue for all the varieties of rice husk based adsorbents tested. RH based adsorbents were compared with the commercially available granular activated carbon. Equilibrium data were satisfactorily fitted to Langmuir and Freundlich isotherms. Kinetic data were fitted to the Pseudo second order model and initial adsorption rates and rate constants were determined.

Fixed bed column studies were conducted for raw rice husk, base washed rice husk and thermally activated rice husk and breakthrough curves were obtained. Bed capacity, breakthrough time, length of the unused bed and time required for full bed exhaustion under ideal condition was calculated from breakthrough curves. Bed capacities for Malachite green and Nylosan blue for thermally treated rice husk were 45 and 30 mg/g respectively. Experimental data obtained from unsteady state fixed bed column studies were used for scale-up calculations and industrial scale fixed bed adsorber dimensions were estimated.

Tests on real textile waste water consists of a mixture of dyes showed that Biological Oxygen Demand (BOD) and Chemical Oxygen Demand (COD) levels can be reduced to 210 mg/l and 30 mg/l respectively using thermally activated rice husk.